

# ADSORPTION AND DESORPTION OF SO<sub>2</sub> ON ACTIVE CARBON

A. Gregório\*, D. Boavida, I. Gulyurtlu and I. Cabrita

\* COALTEC/AMBIENTE e DTC-INETI, Estrada do Paço do Lumiar, 1649-038 Lisboa,  
Portugal Telef: + 351 1 7165299, Fax: + 351 1 7164635

E-mail: [anabela.gregorio@ite.ineti.pt](mailto:anabela.gregorio@ite.ineti.pt)

## Introduction

Activated carbons have been used for many years, quite successfully, for adsorptive removal of impurities from exhaust gas and wastewater streams. They are probably the most versatile of the solid adsorbents, which have chemicals finally distributed on their internal surface and the most widely used for applications in air pollution control and solvent recovery.

The main objective of the present research is to determine whether activated carbon, Commercial or from apricot stones (AC), could be used effectively to adsorb pollutant gas SO<sub>2</sub>, from flue gases.

## Experimental

### *Preparation of Activated Carbons from Apricot stones*

Apricot stones were cracked and sieved at about 2.5 mm. The stones were carbonization in a fluidised bed reactor, at 850°C, in flowing N<sub>2</sub> (3 dm<sup>3</sup>/min), for about 45 min-1 hour and activated at 825°C for two periods of time (8 hours each), in flowing CO<sub>2</sub> (3 dm<sup>3</sup>/min).

### *Characterization of Activated Carbons: Commercial and Apricot stones*

The analyses are given in Table 1.

### *Adsorption and Desorption of SO<sub>2</sub>*

The samples (5 g) were treated with N<sub>2</sub> (600 cm<sup>3</sup>/min) at 400°C for 30 minutes, to remove moisture and impurities. The adsorption occurs at three temperatures (T<sub>ads</sub> = 20, 75 and 150°C), in flowing SO<sub>2</sub> (1400 cm<sup>3</sup>/min). The carbon was then subjected to thermal desorption, in a stream of N<sub>2</sub> (600 cm<sup>3</sup>/min), at heating ramp ranging from adsorption temperature to 400°C. This adsorption/desorption process described was performed two times.

## Results and Discussion

### *Adsorption of SO<sub>2</sub>*

This study showed that the commercial carbon samples present certain instability, when adsorption and desorption occurred at 20°C, since different results were obtained for the three assays carried out. In Figure 1, it can be observed for the fine carbon (FC), that the adsorbed quantity of SO<sub>2</sub> decreases markedly with the increase of the adsorption temperature, as certain author

have described [1,2]. However, for the coarse carbon (CC) this behaviour was not observed. When the amounts of SO<sub>2</sub> adsorbed at 75°C and 150°C are compared, the adsorption amounts at 150°C are slightly higher than the adsorption amounts at 75°C. It can be seen that, the CC adsorbed higher quantity of SO<sub>2</sub> than the FC. It can also be seen that, the amount of SO<sub>2</sub> adsorbed by the activated carbons decreases with increasing number of cycles, conferring what other authors have found [2]. Based on these experimental results, the temperature of 75°C has been selected as the adsorption temperature to carry out the adsorption and desorption process, on the AC.

In Table 2, it can be observed the amounts of SO<sub>2</sub> adsorbed on the Apricot-Carbon (AC) and the differences between the commercial carbon and the AC. The adsorption amounts of SO<sub>2</sub> on the AC were higher than the adsorbed on the commercial carbon, however, this quantity also decreases with increasing number of cycles.

### *Desorption of SO<sub>2</sub>*

In Figure 2, it can be observed that the desorbed quantity of SO<sub>2</sub> decreases markedly with the increase of the adsorption temperature, for the commercial activated carbons (FC and CC). For the temperature of 75°C and 150°C, the desorbed amounts are practically the same. It was also observed that, the FC desorbed more quantity of SO<sub>2</sub> than CC, this difference is more significant at 20°C. Once again, the desorption amount of SO<sub>2</sub> by the activated carbon decreases with increasing number of cycles. The desorption experimental results, obtained in this work are in accordance with previous studies [2], which conferring that the SO<sub>2</sub> can be adsorbed on the activated carbon in two different processes: physisorption (at lower temperature and occurs by one weakly bound on he surface carbon) and chemisorption (at higher temperature and occurs by one strongly bound on he surface carbon). In Table 3 it can seen the number and the temperature peak formation.

In Table 2, it can be observed the amount of SO<sub>2</sub> desorbed from the Apricot-Carbon (AC) and the differences between the commercial Carbon and the AC. The desorption amounts of SO<sub>2</sub> by the AC were higher than those desorbed by the Commercial carbon. However, for the second desorption it was observed that SO<sub>2</sub> desorbed quantity is slightly lower than the quantity desorbed from the second desorption of the commercial

carbon sample. It was observed that this quantity also decreases with increasing number of cycles.

### Conclusions

AC sample adsorbed and desorbed higher quantity of SO<sub>2</sub> from the surface of the carbon than the observed by the Commercial sample. This fact could be attributed to the difference properties, such as surface groups and the porous structure

AC will be the best sample for use in the removed of SO<sub>2</sub> from the exhaustion gases, released in the combustion systems.

### References

1. Lisovskii, A., Shter, G. E., Semiat, R. and Aharoni, C, *Carbon*, 1997; **35** (10-11):1640-1643.
2. Davini, P., *Carbon* 1990; **28** (4): 565-570.

### Acknowledgements

To the group of Prof. Isabel S.Silva of the FCT-UNL for the characterization of the samples. The research described in this work was supported by the project PRAXIS XXI/3/3.1/ENR/18/94.

**Table 1 – Characteristics of the carbon samples**

CARBON	Surface Area B.E.T. (m <sup>2</sup> /g)	Total Pore Vol. (cm <sup>3</sup> /g)	Particle Size (mm)	PZC
Commercial *	1116	0.610	Fine carbon (FC): 0.85 – 1.25 Coarse carbon (CC): 1.25 – 1.70	9.8
Apricot	737	0.186	1 – 1.75	10.4


\* MERCK BDH 33034 4Y

**Table 2 – Resume of the adsorption and desorption amounts of SO<sub>2</sub> on the carbon samples, T<sub>ads</sub> = 75°C**


	Fine Carbon	Coarse Carbon	Apricot-Carbon
1 <sup>st</sup> Adsorption (mg/gC)	9.6	12	21.1
2 <sup>nd</sup> Adsorption (mg/gC)	4.5	5.3	12.7
1 <sup>st</sup> Dedsorption (mg/gC)	2.2	2.4	4.2
2 <sup>nd</sup> Dedsorption (mg/gC)	1.2	1.3	0.9

**Table 3 – Resume of the desorption - temperature peak formation**

Carbon	T <sub>ads</sub> (°C)	Assays	Temperature (°C)
Commercial	20	1 <sup>st</sup> e 2 <sup>nd</sup> Desor.	95 e 300 (Physiso. and Chemisor.)
	75	1 <sup>st</sup> e 2 <sup>nd</sup> Desor.	338 (Physisorption)
	150	1 <sup>st</sup> e 2 <sup>nd</sup> Desor.	338 (Physisorption)
Apricot	75	1 <sup>st</sup> Desor.	146 (Chemisorption)
		2 <sup>nd</sup> Desor.	138 e 297 (Physiso. and Chemisor.)

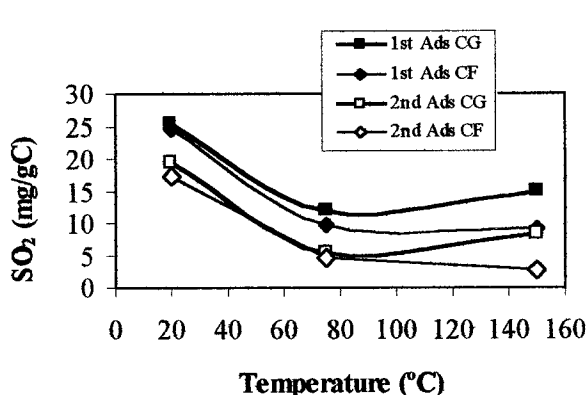

**Figure 1 – Amount of SO<sub>2</sub> adsorbed by the carbon samples at three adsorption temperature.**

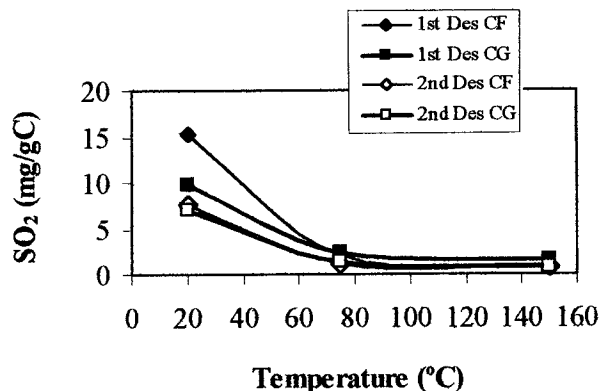

**Figure 2 – Amount of SO<sub>2</sub> desorbed by the carbon samples at three adsorption temperature.**