

EXFOLIATED GRAPHITE FOR ENHANCING THE VIBRATION DAMPING OF CEMENT-MATRIX AND POLYMER-MATRIX STRUCTURAL MATERIALS

Seungjin Han, S. Muthusamy, Po-Hsiu Chen,
Shoukai Wang and D.D.L. Chung

Composite Materials Research Laboratory
University at Buffalo
State University of New York
Buffalo, NY 14260-4400, U.S.A.

Introduction

The damping of mechanical vibration is important for the stability, performance and durability of structures, including aircraft, spacecraft, wind turbines, bridges and buildings. Damping can be achieved by using materials that are capable of the conversion of mechanical energy to heat, so that the mechanical energy is eliminated. This is known as passive damping. As no device is needed, the method is inexpensive. However, this method has been inadequate due to the insufficient ability of available materials for providing the damping. Rubber and other elastomers suffer from inadequate energy dissipation (due to their softness) and the tendency for degradation by UV radiation. Metals such as steel and shape memory alloys are relatively stiff, but they are inadequate in the ability to reduce the vibration amplitude quickly.

This paper innovatively exploits exfoliated graphite for greatly enhancing the damping of cement-based and polymer-based structural materials. The high effectiveness of exfoliated graphite stems from the shear deformation enabled by its accordion microstructure. The use of a structural material for damping is advantageous to the use of a nonstructural material for damping, because structural materials occupy much of the volume of a structure, and the energy dissipation is proportional to the volume. Furthermore, structural materials are durable and cost-effective.

Carbon fiber polymer-matrix composites are dominant aerospace structural materials, but they are poor in damping unless a viscoelastic interlayer is incorporated between the laminae. However, the interlayer decreases the stiffness [1]. This paper provides carbon fiber epoxy-matrix composites that have been modified for enhancing both damping and stiffness through the use of exfoliated graphite at the interlaminar interface. It also provides cement-matrix composites with ultrahigh damping through the incorporation of exfoliated graphite as a network in the cement.

Experimental methods

In case of polymer-matrix composites, exfoliated graphite (as obtained by rapid heating of acid-intercalated natural graphite flake), nanoclay, multi-walled carbon nanotube (MWCNT), single-walled carbon nanotube (SWCNT), and halloysite (clay) nanotube were used alone and in combinations as fillers at every interlaminar interface of a 7-lamina crossply carbon fiber epoxy-matrix composite. The fillers were suspended in a solvent and the suspensions were

applied to the surface of the fiber prepreg. After this, the prepreg sheets were stacked and cured by hot pressing.

In case of cement-matrix composites, exfoliated graphite was mixed with cement particles and the mixture was compressed and then exposed to water for curing. The resulting composite had 8 vol.% graphite, which was in the form of a network (as supported by microscopy and the low electrical resistivity) with the accordion structure typical of exfoliated graphite in each ligament of the network.

For damping evaluation, dynamic mechanical testing was performed under flexure (three-point bending, Perkin-Elmer DMA7) at a controlled loading frequency (0.2 Hz) and room temperature. The testing was performed with the span at 20 mm and the maximum midspan deflection at 5-10 μm .

Results and discussion

Table 1 Dynamic flexural properties of crossply carbon fiber epoxy-matrix composite (0.5 MPa curing, unless stated otherwise).

*0.8 wt.% suspension. †1.2 wt.% suspension. ‡2 wt.% suspension

Interlaminar filler(s) in carbon fiber epoxy-matrix composite	Storage modulus (GPa)	Loss tangent	Loss modulus (GPa)
None	16	0.046	0.73
MWCNT*	35	0.044	1.5
Nanoclay†	21	0.058	1.2
SWCNT*	24	0.058	1.4
Halloysite nanotube*	31	0.054	1.7
Exfoliated graphite	16	0.099	1.6
Exfoliated graphite (2 MPa curing)	20	0.103	2.0
MWCNT* and exfoliated graphite	26	0.074	1.9
Halloysite nanotube‡ and exfoliated graphite	27	0.076	2.0
MWCNT* and nanoclay† (1:3 mass ratio of suspensions)	29	0.072	2.1
Halloysite nanotube‡ and nanoclay† (1:7 mass ratio of suspensions)	31	0.076	2.4
Halloysite nanotube‡ and exfoliated graphite (2 MPa curing)	27	0.12	3.3

Table 1 shows the storage modulus (stiffness), loss tangent and loss modulus (product of the storage modulus and the loss tangent) for the unmodified composite and for composites modified with various interlaminar fillers. The storage and loss moduli are enhanced by any of the interlaminar fillers. Among the five fillers used as sole interlaminar fillers, exfoliated graphite is outstandingly effective in increasing the loss tangent, but the least effective in increasing the storage modulus, whereas MWCNT is the most effective in increasing the storage modulus, but the least effective in increasing the loss tangent. Nanoclay and SWCNT as sole fillers are effective for increasing the loss tangent, though they are less effective than exfoliated graphite. The superiority of exfoliated graphite over nanoclay or SWCNT for increasing the loss tangent is attributed to the accordion

microstructure of exfoliated graphite. MWCNT and halloysite nanotube as sole fillers are most effective for increasing the storage modulus. The combined use of a filler that is effective for enhancing the storage modulus (MWCNT or halloysite nanotube) and one that is effective for enhancing the loss tangent (exfoliated graphite or nanoclay) gives the best performance, as shown by the loss modulus. The combined use of halloysite nanotube and nanoclay gives better performance at a lower cost than the combined use of MWCNT and nanoclay. The combined use of halloysite nanotube and exfoliated graphite also gives better performance at a lower cost than the combined use of MWCNT and exfoliated graphite. Upon increasing the curing pressure from 0.5 to 2 MPa, the exfoliated graphite becomes even more effective, thus causing the combination of halloysite nanotube and exfoliated graphite to give the highest performance, as shown by a loss modulus of 3.3 GPa (350% increase relative to the unmodified composite cured at 0.5 MPa). The increase in curing pressure causes increases in both the storage modulus and the loss tangent. This suggests that a tighter accordion microstructure is attractive for both damping and stiffness. The optimized proportions of the fillers are shown in Table 1 in terms of the mass ratio of the filler suspensions. The superiority of halloysite nanotube over MWCNT is partly because a spreadable suspension with a higher filler concentration can be obtained for halloysite nanotube.

Table 2 Dynamic flexural properties of cement-graphite composite and other materials.

Material	Storage modulus (GPa)	Loss tangent	Loss modulus (GPa)
Cement-graphite	9.3	0.81	7.5
Rubber [2]	0.00745	0.67	0.0067
PMMA [2]	3.63	0.093	0.336
Flexible graphite [3]	1.0	0.19	0.21
Cement paste [4,5]	1.91	0.035	0.067
Cement paste with latex [5]	3.12	0.142	0.443
Cement paste with silica fume [5]	5.76	0.107	0.616

Table 2 shows results for cement-based materials and other materials. The cement-graphite composite is higher in the loss tangent and loss modulus than any of the materials in Tables 1 and 2, although its storage modulus is lower than those of Table 1. Flexible graphite (without cement) [3] is much inferior. The high damping in cement-graphite is attributed to the accordion microstructure in the graphite network (Fig. 1) and the stiffness of the encasing cement.

The cement-graphite composite is effective as a cementitious damping admixture in concrete. Fig. 2 shows the polished surface of cement containing the damping admixture (62 vol.%) and silica fume (15% by mass of cement) at 3 days of curing. The bright regions are the graphite network in a part of a piece of the damping admixture; the dark regions are

cement. The admixture and the cement matrix are in contact, with a diffuse interface.

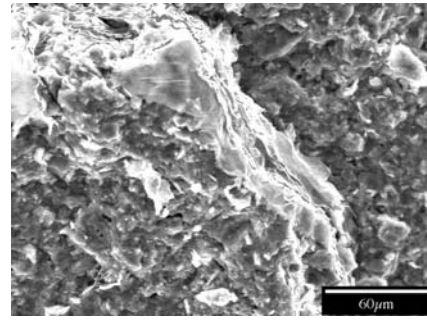


Fig. 1 SEM photograph of the fracture surface of the cement-graphite damping admixture, showing an accordion-structured ligament of the graphite network (bright region).

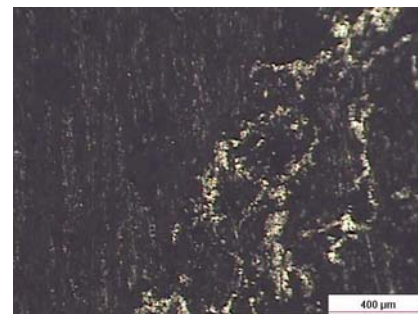


Fig. 2 Optical micrograph of the polished surface of cement containing the cement-graphite damping admixture (62 vol.%) and silica fume (15% by mass of cement) at 3 days of curing.

Conclusions

By using halloysite nanotube and exfoliated graphite as interlaminar fillers in a crossply carbon fiber epoxy-matrix composite, this work has achieved 350% increase in the flexural loss modulus (which reaches 3.3 GPa). The halloysite nanotube is primarily for increasing the storage modulus, while the exfoliated graphite is primarily for increasing the loss tangent. By using exfoliated graphite in cement to form a graphite network with an accordion microstructure in the network ligaments, this work has provided an ultrahigh damping cement-based material (loss modulus 7.5 GPa) that can be used as a damping admixture in concrete.

References

- [1] Segiet M, Chung DDL. Discontinuous surface-treated submicron-diameter carbon filaments as an interlaminar filler in carbon fiber polymer-matrix composites for vibration reduction. *Composite Interfaces* 2000;7(4):257-276.
- [2] Fu W, Chung DDL. Vibration reduction ability of polymers, particularly polymethylmethacrylate and polytetrafluoroethylene. *Polym Polym Compos* 2001;9(6):423-426.
- [3] Luo X, Chung DDL. Vibration damping using flexible graphite. *Carbon* 2000;38:1510-1512.
- [4] Fu X, Chung DDL. Vibration damping admixtures for cement. *Cem Concr Res* 1996;26:69-75.
- [5] Fu X, Li X, Chung DDL. Improving the vibration damping capacity of cement. *J Mater Sci* 1998;33:3601-3605.